

Short Communication

Preparation and Thermoelectric Properties of Nickel Oxide added Strontium Ferrite Nano-Composite

Shin Nishiyama* and Asami Yamada

School of Engineering, Chiba University, Japan

Abstract

NiO added SrFeO_{3-δ} nano-composite bulk was synthesized and its electrical and thermoelectric properties were measured. Seebeck coefficient increased by NiO addition over 400°C. The power factors increased to 97.3Wm⁻¹K⁻², this value is 16 times larger than that of pure SrFeO_{3-δ} samples. The decreased by NiO addition. So, suitable and selected composition seems to make advantage for thermoelectric performance.

Keywords: Oxide Nano-Composite, Seebeck Coefficient, Thermal Conductivity, Thermoelectric Performance

Introduction

Now-a-days, about 70% of all the first energy, generated in combustion electrical power plants, fabricating stands and automobiles are disposed as waste heats without any use. The generated electrical energy was used in homes, public transportations and companies, and there also the waste heat was generated. Using these abundant large energies makes many solutions, such as the exhaustion of oil sources problem and the global warming problems. However, it is difficult to retrieve wide small spread energies from the around environment. In order to retrieve these waste heats, the thermoelectric system plays an important role, because it is the direct conversion of the heat energy to the electrical one by Seebeck effects without any toxic and warming gases. And the system has also the features of the maintenance free, high density of the energy outputs and compactness. Furthermore it is reported nano-finerising and low-dimensioning makes drastic increasing of performances because of the quantum effects [1], so many exams were tried such as nanodots [2], nanowiyers [3], nanomaterials [4], and nanocomposites [5]. However, the technologies to fabricate

*Corresponding authors: Shin Nishiyama, School of Engineering, Chiba University, Japan, E-mail: shin@faculty.chiba-u.jp

Citation: Nishiyama S, Yamada A (2019) Preparation and Thermoelectric Properties of Nickel Oxide added Strontium Ferrite Nano-Composite. J Mod Chem Sci 3: 004.

Received: June 07, 2019; Accepted: June 18, 2019; Published: June 25, 2019

Copyright: © 2019 Nishiyama S and Yamada A. This is an open-access article distributed under the terms of the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited.

nanodots and superlattices, and molecular beam epitaxy are time and cost consuming, so the practical use thought to be difficult.

NiO was not so soluble in transition metals [6]. In this study, SrFeO_{3-δ} bulk polycrystalline samples and NiO nano-particles composite samples were prepared by an ordinally method and effects of NiO addition on the thermoelectric properties were investigated. The electrical conductivities and Seebeck coefficients of these ceramics samples were measured and the thermal conductivities of the part of the samples were also measured.

Materials and Methods

As the starting materials, SrCO₃ (purity was 99.99), Fe₂O₃ (99.9), and NiO 99.9, all chemicals were purchased by Wako Junyaku Industry, Japan) were used. NiO was grinded into nano-particles at 900rpm for 2 h in zirconia pod with EtOH. And then SrCO₃ and Fe₂O₃ were weighed with the grinded NiO powders so as to be SrFeO₃ + (NiO) × (x = 0, 0.03, 0.05, 0.10, 0.20) and mixed for 1 h using an alumina pestle and mortar with acetone. The dried mixed powders were placed in an alumina crucible, calcined at 1000°C for 8 h. The obtained calcined body was wet pulverized with acetone for 1 h. Approximately 0.6 g of calcined powders were uniaxially pressed at 100 MPa for 5 min, then the samples were cold isostatic pressed at 700 MPa for 10 min. The obtained compact was sintered at 1100°C for 8 h. The sintered bodies obtained as the bar-like samples were polished. In order to confirm chemical composition and nano-composition, an XRD and a SEM-EDS apparatus were used.

For conductivity measurements and Seebeck coefficient measurements, a rectangular sample of about 2 times 4 mm was polished by a sand paper. After a constant DC current was applied, the current versus the measured voltage, the cross-sectional area of the samples, and the distances between the two platinum wires were measured, and then the conductivities were calculated. The Seebeck coefficient was determined when the temperature of both ends of the samples became stable using an air pump. The temperature difference versus Seebeck voltage was plotted, and the slope was taken as the relative Seebeck coefficient. The absolute Seebeck coefficient of the sample was obtained by subtracting the absolute Seebeck coefficient of platinum from the relative Seebeck coefficient of the sample. For the thermal conductivity measurement, samples shaped and sintered so as to have a thickness of about 2 mm using a 15 mm × 15 mm square mold were used. The surface was polished in the same manner as the samples for electrical property measurement. From the measured thermal diffusivity, specific heat, and material density, the thermal conductivity was calculated.

Results and Discussion

Figure 1 shows XRD results. The tetragonal perovskite type Sr-FeO₃ was confirmed in all the samples prepared. In the sample with 5 mol% find the small NiO peaks which can be seen clearly at more NiO samples. And no NiO peak was confirmed with the 3 mol% sample. So, Ni ion should exist as the solid solution below that concentration.

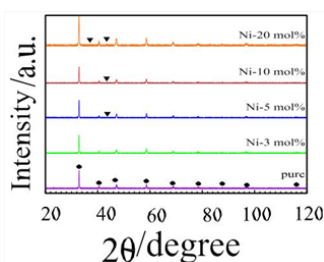


Figure 1: XRD patterns of $SrFe_{1-x}Ni_xO_3$ ($0 \leq x \leq 20$). ● is $SrFeO_3$ phase, ▼ is NiO phase.

Figure 2 shows the results of line analysis of SEM-EDS. At the position of the nano-particles at the grain boundary of the matrix phase, the peak of Ni atom was confirmed, and point analysis of fine particles between bulks showed the ratio of Ni was high. At the same time, the ratio of Sr and Fe was high in bulks and Ni was low. Sr and Fe are detected at the location of Ni. It is believed that EDS used X-ray and could not look information in the depth direction. Combined with the results of XRD, it was confirmed that nano composite was fabricated by this procedure.

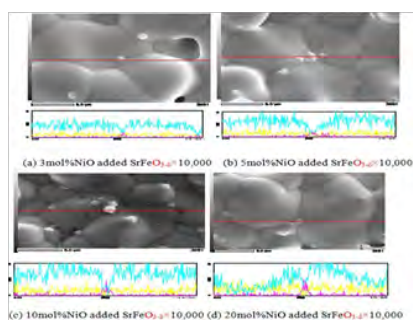


Figure 2: SEM images and line profiles of elements. Cyan, yellow, magenta correspond to Sr, Fe, and Ni, respectively.

Figure 3 shows the temperature dependence of the conductivities of the samples. Those of all measured samples increased with temperature up to about 400°C, then reversed and decreased. This is thought to be due to the formation of oxygen deficiency of $SrFeO_{3-\delta}$ at about 400°C. In the sample with the addition amount of 10 mol% or less, the conductivity showed almost the same value as that of the sample without addition, but in the sample added with 20 mol%, the conductivity was lower than that of the sample not added in the whole measured temperature range.

Figure 4 shows the temperature dependence of the Seebeck coefficient of the same sample. All specimens increased with temperature, and the tendency was remarkable over 400°C. Also, by adding NiO, the Seebeck coefficient over 400°C was greatly improved, and in the measured temperature range the higher the temperature, the more remarkable the tendency appeared. Furthermore, it was found that the addition of NiO lowers the thermal conductivity at room temperature.

Table 1 shows the results of the thermal conductivity of a sample containing 5 mol% of NiO with different particle sizes. Samples obtained by pulverizing NiO with a planetary ball mill at 900 rpm for 2 h showed lower values than samples not pulverized. It is thought

that the small NiO particles at grain boundaries exist as the scattering center of phonon transportation, and the effect was higher as the particle was finer. In addition, it can be considered that addition of NiO suppressed grain growth of the base material.

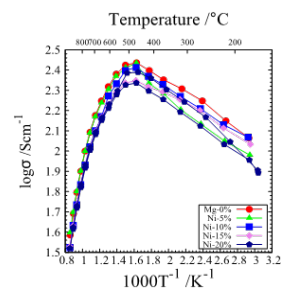


Figure 3: Temperature dependence of the electrical conductivity (σ) of $SrFe_{1-x}Ni_xO_3$ ($0 \leq x \leq 20$) samples.

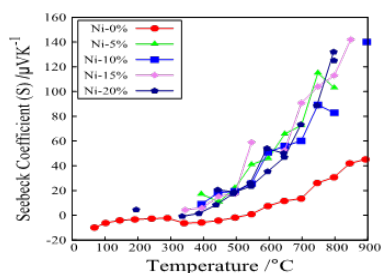


Figure 4: Temperature dependence of Seebeck coefficient (S) of $SrFe_{1-x}Ni_xO_3$ ($0 \leq x \leq 20$) samples.

	Specific heat(J/gK)	Thermal diffusivity (cm ² /sec)	Density (g/cm ³)	Thermal conductivity (W/mK)
Ni-5mol% (un milled)	7.529×10^{-2}	1.060×10^{-1}	4.668	3.725
Ni-5mol% (900rpm, 2h)	4.765×10^{-2}	1.127×10^{-1}	4.676	2.511

Table 1: Particle size dependence on thermal conductivity.

Conclusion

Nano-composite bulk materials of $SrFeO_{3-\delta}$ plus NiO were prepared by solid state reaction. Electrical properties and thermal conductivity of these materials were measured to evaluate thermoelectric characteristics. Samples with 5 mol% NiO showed a conductivity of 61.1 Sm^{-1} at 793°C and Seebeck coefficient of 112 VK^{-1} , so the output power factor was $97.3 \mu\text{Wm}^{-1}\text{K}^{-2}$. This is a 16 times larger than that of pure $SrFeO_{3-\delta}$ at the same temperature. Furthermore, it was found that by adding NiO of nano-particles, thermal conductivity can be lowered without changing electrical properties.

References

- Dresselhouse MS, Chen G, Tang MY, Yang R, Lee H, et al. (2007) New directions for low-dimensional thermoelectric materials. *Advanced Materials* 19: 1043-1053.

2. Hsu KF, Loo S, Guo F, Chen W, Dyck JS, et al. (2004) Cubic AgPb(m)SbTe(2+m): Bulk thermoelectric materials with high figure of merit. Science 303: 818-821.
3. Boukai AI, Bunimovich Y, Tahir Kheli J, Yu JK, Goddard III WA, et al. (2008) Silicon nanowires as efficient thermoelectric materials. Nature 451: 168-171.
4. Poudel B, Hao Q, Ma Y, Lan Y, Minnich A, et al. (2008) High-thermoelectric performance of nanostructured bismuth antimony telluride bulk alloys. Science 320: 634-638.
5. Wang H, Hwang J, Snedaker ML, Kim IH, Kang C, et al. (2015) High thermoelectric performance of a heterogeneous PbTe nano-composite. Chem Mater 27: 944-949.
6. Mandal SK, Das AK, Nath TK, Karmakar D (2006) Applied Physics Letters 89: 144105.



Journal of Anesthesia & Clinical Care
Journal of Addiction & Addictive Disorders
Advances in Microbiology Research
Advances in Industrial Biotechnology
Journal of Agronomy & Agricultural Science
Journal of AIDS Clinical Research & STDs
Journal of Alcoholism, Drug Abuse & Substance Dependence
Journal of Allergy Disorders & Therapy
Journal of Alternative, Complementary & Integrative Medicine
Journal of Alzheimer's & Neurodegenerative Diseases
Journal of Angiology & Vascular Surgery
Journal of Animal Research & Veterinary Science
Archives of Zoological Studies
Archives of Urology
Journal of Atmospheric & Earth-Sciences
Journal of Aquaculture & Fisheries
Journal of Biotech Research & Biochemistry
Journal of Brain & Neuroscience Research
Journal of Cancer Biology & Treatment
Journal of Cardiology: Study & Research
Journal of Cell Biology & Cell Metabolism
Journal of Clinical Dermatology & Therapy
Journal of Clinical Immunology & Immunotherapy
Journal of Clinical Studies & Medical Case Reports
Journal of Community Medicine & Public Health Care
Current Trends: Medical & Biological Engineering
Journal of Cytology & Tissue Biology
Journal of Dentistry: Oral Health & Cosmesis
Journal of Diabetes & Metabolic Disorders
Journal of Dairy Research & Technology
Journal of Emergency Medicine Trauma & Surgical Care
Journal of Environmental Science: Current Research
Journal of Food Science & Nutrition
Journal of Forensic, Legal & Investigative Sciences
Journal of Gastroenterology & Hepatology Research
Journal of Gerontology & Geriatric Medicine
Journal of Genetics & Genomic Sciences
Journal of Hematology, Blood Transfusion & Disorders
Journal of Human Endocrinology
Journal of Hospice & Palliative Medical Care
Journal of Internal Medicine & Primary Healthcare
Journal of Infectious & Non Infectious Diseases
Journal of Light & Laser: Current Trends
Journal of Modern Chemical Sciences
Journal of Medicine: Study & Research
Journal of Nanotechnology: Nanomedicine & Nanobiotechnology
Journal of Neonatology & Clinical Pediatrics
Journal of Nephrology & Renal Therapy
Journal of Non Invasive Vascular Investigation
Journal of Nuclear Medicine, Radiology & Radiation Therapy
Journal of Obesity & Weight Loss
Journal of Orthopedic Research & Physiotherapy
Journal of Otolaryngology, Head & Neck Surgery
Journal of Protein Research & Bioinformatics
Journal of Pathology Clinical & Medical Research
Journal of Pharmacology, Pharmaceutics & Pharmacovigilance
Journal of Physical Medicine, Rehabilitation & Disabilities
Journal of Plant Science: Current Research
Journal of Psychiatry, Depression & Anxiety
Journal of Pulmonary Medicine & Respiratory Research
Journal of Practical & Professional Nursing
Journal of Reproductive Medicine, Gynaecology & Obstetrics
Journal of Stem Cells Research, Development & Therapy
Journal of Surgery: Current Trends & Innovations
Journal of Toxicology: Current Research
Journal of Translational Science and Research
Trends in Anatomy & Physiology
Journal of Vaccines Research & Vaccination
Journal of Virology & Antivirals
Archives of Surgery and Surgical Education
Sports Medicine and Injury Care Journal
International Journal of Case Reports and Therapeutic Studies

Submit Your Manuscript: <http://www.heraldopenaccess.us/Online-Submission.php>